

2019

Primary Dendrite Trunk Diameter in Al-7wt% Si Alloy Directionally Solidified Aboard the International Space Station

S. R. Upadhyay

RioTinto Kennecott Copper

Surendra N. Tewari

Cleveland State University

M. Ghodes

Middle East Technical University


R. N. Grugel

NASA-Marshall Space Flight Center

D. R. Poirier

University of Arizona

Follow this and additional works at: https://engagedscholarship.csuohio.edu/encbe_facpub

 [a next page for additional authors](#)

Part of the [Chemical Engineering Commons](#), and the [Materials Science and Engineering Commons](#)

How does access to this work benefit you? Let us know!

Original Citation

SR Upadhyay et al 2019 IOP Conf. Ser.: Mater. Sci. Eng. 529 012022

Repository Citation

Upadhyay, S. R.; Tewari, Surendra N.; Ghodes, M.; Grugel, R. N.; Poirier, D. R.; and Lauer, M., "Primary Dendrite Trunk Diameter in Al-7wt% Si Alloy Directionally Solidified Aboard the International Space Station" (2019). *Chemical & Biomedical Engineering Faculty Publications*. 167.

https://engagedscholarship.csuohio.edu/encbe_facpub/167

This Conference Paper is brought to you for free and open access by the Chemical & Biomedical Engineering Department at EngagedScholarship@CSU. It has been accepted for inclusion in Chemical & Biomedical Engineering Faculty Publications by an authorized administrator of EngagedScholarship@CSU. For more information, please contact library.es@csuohio.edu.

Authors

S. R. Upadhyay, Surendra N. Tewari, M. Ghodes, R. N. Grugel, D. R. Poirier, and M. Lauer

PAPER • OPEN ACCESS

Primary Dendrite Trunk Diameter in Al-7wt% Si Alloy Directionally Solidified Aboard the International Space Station

To cite this article: SR Upadhyay *et al* 2019 *IOP Conf. Ser.: Mater. Sci. Eng.* **529** 012022

View the [article online](#) for updates and enhancements.

Primary Dendrite Trunk Diameter in Al-7wt% Si Alloy Directionally Solidified Aboard the International Space Station

SR Upadhyay¹, SN Tewari², M Ghodes³, RN Grugel⁴, DR Poirier⁵ and M Lauer⁶

¹ Engineer-Metallurgical, RioTinto Kennecott Copper, 11600 W. 2100 South, Magna (UT) USA.

² Professor, Chemical and Biomedical Engineering Department, Cleveland State University, Cleveland, OH (44115) USA.

³ Assistant Professor, Middle East Technical University, Northern Cyprus Campus, Güzelyurt, Mersin 10, Turkey

⁴ Scientist, NASA-Marshall Space Flight Center, Huntsville, AL (35812) USA

⁵ Professor, Department of Materials Science and Engineering, The University of Arizona, Tucson, AZ (85721) USA

⁶ Engineer, ME Elecmetal Inc., Duluth, MN (55808) USA

E-mail: S.Tewari@csuohio.edu

Abstract. Under a NASA (National Aeronautics and Space Agency)-ESA (European Space Agency) collaborative research project, MICAST (Microstructure formation in casting of technical alloys under a diffusive and magnetically controlled convection conditions), three Al-7wt% Si samples (MICAST-6, MICAST-7 and MICAST2-12) were directionally solidified at growth speeds varying from 10 to 50 $\mu\text{m s}^{-1}$ aboard the International Space Station to determine the effect of mitigating convection on the primary dendrite array. The observed primary dendrite trunk diameters during steady-state growth of MICAST samples show a good agreement with predictions from a coarsening based model developed by the authors. The trunk diameters in the terrestrial-grown equivalent samples were larger than those predicted from the model. This suggest that thermosolutal convection increases the trunk diameter of primary dendrites, perhaps by increasing their tip radius due to compositional changes.

1. Introduction

During directional solidification (DS) of alloys in a positive thermal gradient (G_L) a mushy-zone consisting of array of primary dendrite arms and interdendritic liquids in between, develops between the melt above and the solid below. Analytical and numerical theories have been developed to describe various aspects of the dendrite network, e.g., cell to dendrite transition, dendrite tip radius and primary dendrite spacing [1-8] under diffusive growth conditions. Given that mechanical properties depend upon the dendrite spacing and distribution, numerous experiments have been carried out to measure primary spacing as a function of solute content (C_0), growth speed (R), thermal gradient (G_L) and the physical properties of the alloy to compare with model predictions [9-27]. Invariably the discrepancy between the experimental observations and model predictions has been attributed to convection in the melt. Convection itself has been treated by a pseudo-analytical approach of defining an overall mushy-zone Rayleigh Number for the growth conditions [28-40], and correlating, for example, the increasing propensity for convection with observed reduction in mean spacing in terrestrial-grown samples as



Content from this work may be used under the terms of the [Creative Commons Attribution 3.0 licence](#). Any further distribution of this work must maintain attribution to the author(s) and the title of the work, journal citation and DOI.

compared with those solidified in microgravity [30-33, 40]. While primary spacing has been extensively evaluated as the morphology parameter for the dendritic arrays, another feature, the primary dendrite trunk-diameter [41-44] has remained relatively unexplored. The trunk-diameter responds to an abrupt speed change more quickly because it is more reflective of the dendrite tip radius as compared with the primary spacing which achieve the new steady-state value only after further DS for two to three mushy-zone length [45]. Here we present primary dendrite trunk diameter measurements from three Al-7Si alloy samples (MICAST6, MICAST-7 and MICAST2-12), which were directionally solidified on the Space Station at growth speeds varying from 5 to 50 $\mu\text{m s}^{-1}$. It is seen that the observed primary dendrite trunk-diameters during steady-state growth of MICAST samples are in a good agreement with predictions from a coarsening based model developed by some of the authors [44].

2. Experiments

Cylinders with a diameter of 7.8 mm and a length of ~25-cm were machined from [100] oriented terrestrially grown dendritic Al-7Si samples and inserted into alumina ampoules kept within the Sample Cartridge Assembly (SCA) inserts of the Low Gradient Furnace (LGF) for MICAST-6 and MICAST-7 and in the Specimen Quench Furnace (SQF) for MICAST2-12. The Al-7Si cylinders were partially remelted in space and directionally solidified by withdrawing the furnace with respect to the SCA; their unmelted solid portions at cold end acted as [100] oriented seed. Fig. 1 shows a schematic representation of the solidification processing conditions. The unmelted portion is left of T_E (eutectic isotherm) with the melted and directionally solidified portion on the right. The mushy-zone lengths at the onset of DS are indicated in the figure. For MICAST-6 the withdrawal speed was 5 $\mu\text{m s}^{-1}$ for 3.75 cm, and then 50 $\mu\text{m s}^{-1}$ for rest of the 11.2 cm long melt. For MICAST-7 it was 20 $\mu\text{m s}^{-1}$ for 8.5 cm and then 10 $\mu\text{m s}^{-1}$ for the rest 10.5 cm. For MICAST2-12 it was 40 $\mu\text{m s}^{-1}$ along its entire 12 cm long melt column.

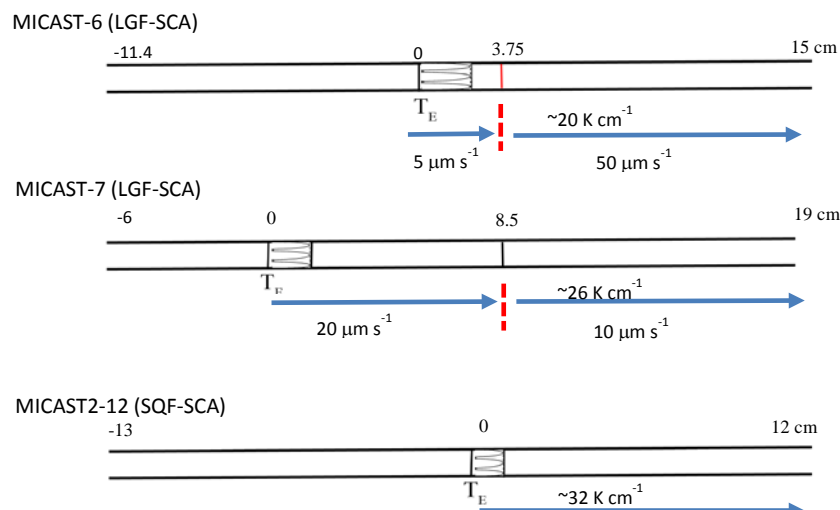


Figure 1. Solidification processing conditions of the MICAST samples. The unmelted portion is left-of eutectic temperature (T_E) with the melted and directionally solidified portion on the right. The mushy-zone lengths at the onset of directional solidification are indicated near T_E .

Temperatures along the sample length during DS were recorded by eleven thermocouples which were attached at regular intervals on the outer surface of the alumina ampoules along their length. Growth speeds and thermal gradients extracted from such thermal profiles are plotted in Fig. 2 for the MICAST-6, MICAST-7 and MICAST2-12 samples. Fig. 2(a), on the left, plots the thermal gradients at the liquidus (G_{TL}) (solid lines) and at the eutectic (G_{TE}) (dashed lines) temperature as a function of distance from the cold end of the samples. Fig. 2(b), on the right, plots the liquidus (V_{TL}) and eutectic (V_{TE}) isotherm velocities along the sample lengths. The thermal gradients were observed to vary during

directional solidification. For example G_{TL} varied from 22 to 14 $K\ cm^{-1}$ during growth of MICAST-6, from 26 to 24 $K\ cm^{-1}$ for MICAST-7, and from 33 to 31 $K\ cm^{-1}$ for MICAST2-12.

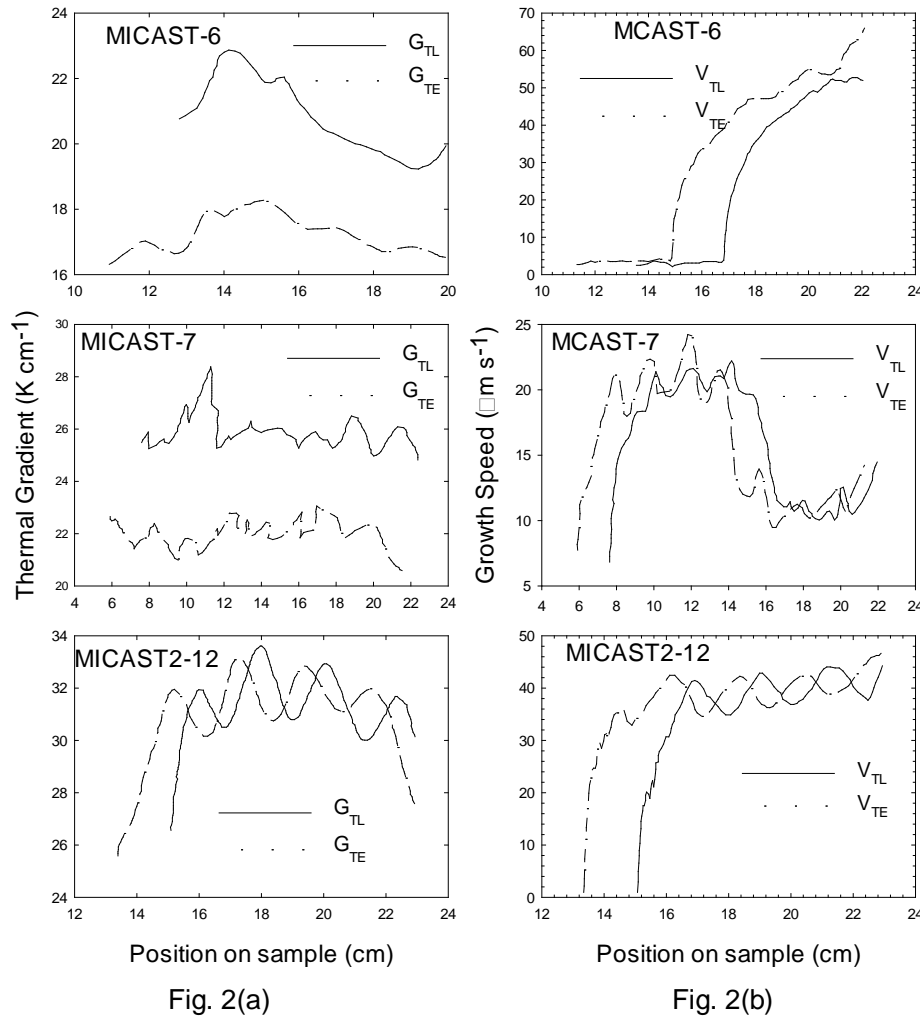


Figure 2. Thermal gradients at liquidus (G_{TL}) and at eutectic (G_{TE}) (Figs. 2(a) on the left), and velocities of liquidus (V_{TL}) and eutectic (V_{TE}) isotherms (Figs. 2(b) on the right) as a function of distance from the sample bottom during directional solidification of MICAST-6, MICAST-7 and MICAST2-12 samples.

3. Results

Fig.3 shows typical transverse microstructures along the lengths of the MICAST samples. Trunk diameters of primary dendrites on several such cross-sections along the length of the three MICAST samples were measured in the manner describes in Ref. 44. Figure 4 shows the variation in the primary dendrite-trunk diameter along the length of the three samples. Circles are average primary dendrite trunk diameter and error bars are the \pm standard deviation; the dotted lines are predictions from a model proposed by the authors [44]. Recall that for the MICAST-6 samples there was a step increase in the growth speed from 5 to 50 $\mu m\ s^{-1}$ at the distance of 3.75 cm (Fig. 1(a)) and for the MICAST-7 sample an abrupt decrease from 20 to 10 $\mu m\ s^{-1}$ at 8.5 cm (Fig. 1(b)). The entire 12 cm long melted portion of MICAST2-12 sample was grown at 30 $\mu m\ s^{-1}$ (Fig. 1(c)). The trunk-diameters respond to the speed

changes almost immediately. Also, the predictions from the simple coarsening-based trunk-diameter model [44] are in a good agreement with the experimental observations during the transient and the steady-state DS.

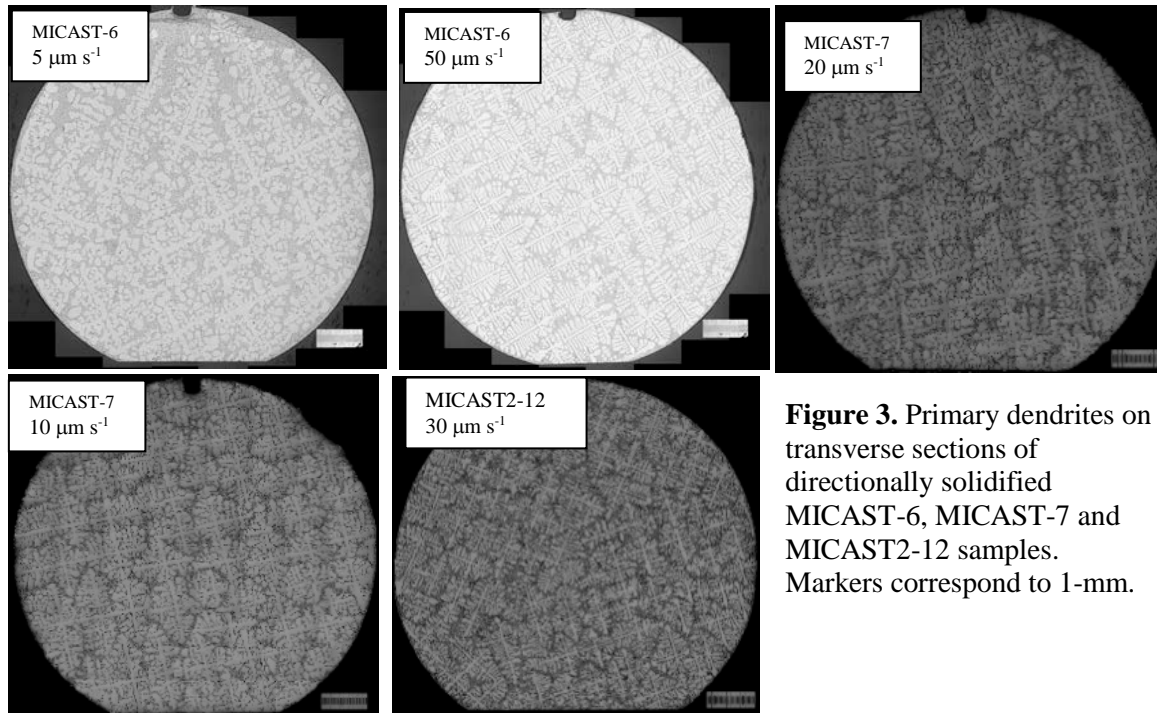


Figure 3. Primary dendrites on transverse sections of directionally solidified MICAST-6, MICAST-7 and MICAST2-12 samples. Markers correspond to 1-mm.

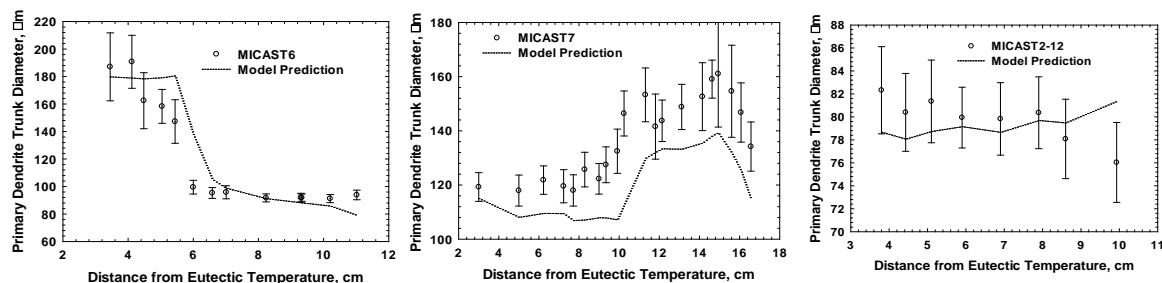


Figure 4. Primary dendrite trunk diameters along the DS length of MICAST-6, MICAST-7 and MICAST2-12 samples. Symbols are average values and error bars are \pm one standard deviation; the dotted lines are predictions from a model proposed by the authors [44].

If we include data only from the steady-state DS portion of the MICAST samples, the agreement appears to be even better (Fig. 5). For each growth speed the trunk-diameter measurements from only those transverse sections were pooled together which met the following conditions, (i) at least, 2-mushy zone lengths of directional solidification has occurred at one growth speed, (ii) at least, 2-mushy zone lengths of solid exists below T_E , and, also at least 2-mushy zone lengths of liquid exists above T_E . Fig.5 shows that predictions from the model (the dotted line) are in a very good agreement with the observed trunk diameters (symbols and \pm standard deviation).

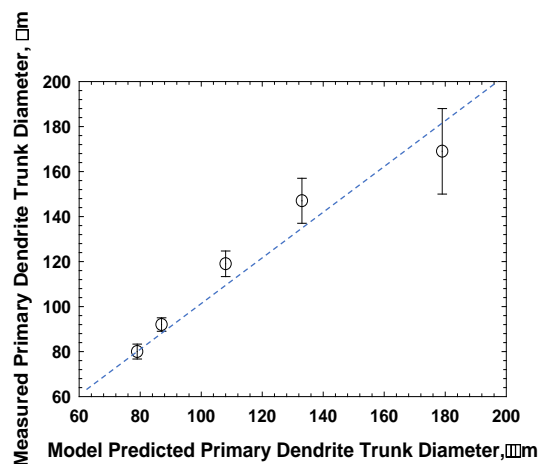


Figure 5. Comparison of the experimentally observed primary trunk diameters during steady-state directional solidification conditions in the MICAST-6, MOCAS-7, and MICAST2-12 samples with those predicted from a model proposed by the authors [44].

4. Discussion and Conclusion

Following additional observations were made during this study, details of which are not included in this paper because of the lack of space. The MICAST samples grown at 10, 20, 30 and 50 $\mu\text{m s}^{-1}$ did not show the radial macrosegregation which invariably occurs during terrestrial DS of Al-7Si alloy [46] and is attributed to the “steeping” type thermosolutal convection [28-32, 46]. This strongly suggests that the three MICAST samples were indeed directionally solidified under convection-free diffusive transport conditions. We have also seen that primary dendrite trunk diameters in the Al-7Si samples, which were directionally solidified terrestrially under approximately similar growth conditions as the low-g processed MICAST samples, are larger than those predicted from the model. These observations strongly suggest that the thermosolutal convection during directional solidification not only reduces the spacing between primary dendrites [30-33] it also increases their trunk diameter as compared with growth under diffusive transport conditions, perhaps by increasing their tip radius.

5. References

- [1] Burden MH and Hunt JD 1974 *J. Crystal Growth* **22** 99-108.
- [2] Kurz W and Fisher DJ 1979 *Int. Metall. Rev.* **5(6)** 177-204.
- [3] Trivedi R 1980 *J. Cryst. Growth* **49** 219-232.
- [4] Hunt JD 1979 *Solidification and Casting of Metals*, The Metals Society, London, 3.
- [5] Trivedi R 1984 *Metall. Trans. A* **15A** 977-984.
- [6] Lu SZ and Hunt JD 1992 *J. Cryst. Growth* **123** 17-34.
- [7] Hunt JD and Lu SZ 1996 *Metall. Mater. Trans.* **27A** 611-23.
- [8] Takaki T, Sakane S, Ohno M, Shibuta Y, Shimokawabe T, Aoki T 2016 *Acta Materi.* **118** 230-243.
- [9] Klaren CM, Verhoeven JD and Trivedi R 1980 *Metall. Trans.* **11A** 1853-1861.
- [10] McCartney DG and Hunt JD 1981 *Acta Met.* **29** 1851-1863.
- [11] Mason JT, Verhoeven JD and Trivedi R 1982 *J. Cryst. Growth* **59** 516-524.
- [12] Somboonsuk K, Mason JT and Trivedi R 1984. *Metall. Trans.* **15A** 967-975.
- [13] Miyata Y, Suzuki T and Uno J 1985 *Metall. Trans.* **16A** 1779-1814.
- [14] Chopra MA and Tewari SN 1991 *Metall. Trans.* **22A** 2467-2474.
- [15] Billia B, Jamgotchian H, Thi HN 1991 *Metall. Trans.* **22A** 3041-3050.
- [16] Noel N, Jamgotchian H, and Billia B 1997 *J. Crystal Growth.* **181** 117-132.
- [17] Odell SP, Ding GL and Tewari SN 1999 *Metall. Mater. Trans.* **30A** 2159-2165.
- [18] Hui J, Chen R, Tiwari R, Wu X, Tewari SN and Trivedi R 2002 *Metall. Mater. Trans.* **33A** 3499-3510.
- [19] Trivedi R, Mazumder P and Tewari SN 2002 *Metall. Mater. Trans.* **33A** 3763-3775.

- [20] Tschopp MA, Miller JD, Oppedal AL and Solanki KN 2014 *Metall. Mater. Trans.* **45A** 426-437.
- [21] Chopra MA and Tewari SN 1991 *Metall. Trans.* **22A** 2467-2474.
- [22] Han SH and Trivedi R 1994 *Acta Metall. Mater.* **42** 25-41.
- [23] Tewari SN, Weng YH, Ding GL and Trivedi R 2002 *Metall. Mater. Trans.* **33A** 1229-1243.
- [24] Gunduz M and Cardili E 2002 *Mater. Sci. Eng. A* **3127** 167-185.
- [25] Tewari SN and Laxmanan V 1987 *Acta Met.* **35** 175-183.
- [26] Trivedi R and Somboonsuk K 1984 *Matls. Sci. Engg.* **65** 65-74.
- [27] Esaka H and Kurz W 1984 *J. Cryst. Growth* **69** 362-366.
- [28] Dupouy MD, Camel D and Favier JJ 1989 *Acta. Metall. Mater.* **37**[4] 1143-1157.
- [29] Dupouy MD, Camel D and Favier JJ 1992 *Acta Metall Mater.* **40**[7] 1791-1801.
- [30] Dupov MD and Camel D 1998 *J. Crystal Growth.* **183** 469-489.
- [31] Thi HN, Dabo Y, Drevet B, Dupouy MD, Camel D, Billia B, Hunt JD and Chilton A 2005 *J. Cryst. Growth* **281** 654-668.
- [32] Drevet B, Thi HN, Camel D, Billia B and Dupouy MD 2000 *J. Cryst. Growth.* **218** 419-433.
- [33] Tewari SN and Shah R 1996 *Metall. Trans.* **27A** 1353-1361.
- [34] Beckermann C, Gu JP, and Boettinger WJ 2000 *Metall. Mater. Trans.* **31A** 2545-52.
- [35] Tewari SN, Tiwari R and Magadi G 2004 *Metall. Mater. Trans.* **35A** 2927-2934.
- [36] Tewari SN and Tiwari R 2003 *Metall. Mater. Trans.* **34A** 2365-2376.
- [37] Ojha SN, Ding G, Lu Y, Rye J and Tewari SN 1999 *Metall. Mater. Trans.* **30A** 2167-2171.
- [38] Tewari SN, Shah R and Chopra MA 1993 *Metall. Mater. Trans.* **24A** 1661-1669.
- [39] Ojha SN and Tewari SN 2000 *Int. J. Cast Metals Res.* **13** 207-213.
- [40] Zimmerman G and Weiss A 2005 *Microg. Sci. Techn.* **XVI** 143-147.
- [41] Grugel RN 1992 *Materials Characterization* **28** 213-219.
- [42] Grugel RN 1995 *Metall. Mater. Trans.* **26A** 496-499.
- [43] Pratt RA and Grugel RN 1993 *Materials Characterization* **30** 225-231.
- [44] Tewari SN, Grugel RN and Poirier DR 2014 *Metall. Materials. Trans.* **45A** 4758-4761.
- [45] Hui J, Chen YS, Wu X and Tewari SN 2003 *J. Cryst. Growth*, **253** 413-423.
- [46] Ghods M, Johnson L, Lauer M, Tewari SN, Grugel RN and Poirier DR 2016 *J. Cryst. Growth*, **441** 107-116.

Acknowledgements

This research was supported by NASA-Grants (NNX08AN49G and NNX14AJ73G). Appreciation is expressed to all the scientists and engineers from NASA and ESA whose combined effort made this research possible, and to Dr Men G. Chu (ALCOA) for providing the Al-7Si alloy feed-stock.