

8-26-2009

Destruction, Amorphization and Reactivity of Nano-BN Under Ball Milling

A. N. Streletskii
Russian Academy of Sciences

D. G. Permenov
Federal State Unitary Enterprise

B. B. Bokhonov
Russian Academy of Sciences

I. V. Kolbanev
Russian Academy of Sciences

A. V. Leonov
Moscow State University

See next page for additional authors

Follow this and additional works at: https://engagedscholarship.csuohio.edu/sciphysics_facpub

 Part of the [Physics Commons](#)

[How does access to this work benefit you? Let us know!](#)

Repository Citation

Streletskii, A. N.; Permenov, D. G.; Bokhonov, B. B.; Kolbanev, I. V.; Leonov, A. V.; Berestetskaya, I. V.; and Streletzky, Kiril A., "Destruction, Amorphization and Reactivity of Nano-BN Under Ball Milling" (2009). *Physics Faculty Publications*. 253.
https://engagedscholarship.csuohio.edu/sciphysics_facpub/253

This Article is brought to you for free and open access by the Physics Department at EngagedScholarship@CSU. It has been accepted for inclusion in Physics Faculty Publications by an authorized administrator of EngagedScholarship@CSU. For more information, please contact library.es@csuohio.edu.

Authors

A. N. Streletskii, D. G. Permenov, B. B. Bokhonov, I. V. Kolbanev, A. V. Leonov, I. V. Berestetskaya, and Kiril A. Streletzky

Destruction, amorphization and reactivity of nano-BN under ball milling

A.N. Streletskii , D.G. Permenov , B.B. Bokhonov , I.V. Kolbanov , A.V. Leonov ,
I.V. Berestetskaya , K.A. Streletsky

Introduction

Hexagonal boron nitride (h-BN) is analogous to graphite in its crystallographic parameters. The structure of h-BN is presented by layers of flat B_3N_3 hexagons packed in the $[001]$ direction with alternating nitrogen and boron atoms one over another. There is a metastable turbostratic BN (t-BN) [1] in which hexagon layers are located in parallel to each other, but azimuthal disposition of hexanes is chaotic. The disorder in the disposition of hexagon layers results in enlarged interlayer distance d_{002} .

The mechanical activation of h-BN is promising for production of superhard cubic BN [2], nanotubes [3], creation of layered composites [4], etc. The first data about processes taking place under ball milling of h-BN are given in [2–6]. This paper studies the mechanisms of h-BN mechanical activation and the onset of chemical activity as a result of mechanical treatment.

Experimental techniques

Mechanochemical activation was carried out in a vibration ball mill with vials and balls made of hardened bearing steel under protective Ar atmosphere. The ball-to-powder weight ratio was 60:1. The depth of mechanical activation was

characterized by the dose D of energy supplied to the material under milling instead of widely used milling time [7]. The dose (J/g) is defined as $D = Jt$, where J is specific power intensity of the mill and t is milling time. The value of J was 36 W/g.

Mechanochemical hydrogenation was carried out in a laboratory vibration mill, hermetically joined to a vacuum device. The H_2 absorption was measured by the pressure fall in known volume [8]. The H_2 pressure was $(3-5) \times 10^4$ Pa. Power intensity of the mill was 1 W/g.

Structural characterization of milled samples was performed by X-ray diffraction (XRD) with monochromatized $Cu\ K\alpha$ radiation (DRON-3 device). Values of coherent scattering region (CSR), L , and microstresses, ϵ , were calculated on the basis of the line profile analysis of X-ray spectra using Ref [9]. For very broad lines the L value was estimated using Sherrer's formula. Specific surface area of the powders was determined using the low-temperature (77 K) BET Ar adsorption technique. Measurements by transmission electron microscopy (TEM) were carried out on an electron microscope Jeol JEM 2000 FX II. Fourier Transformation Infra Red (FTIR) spectroscopy measurement used AF-1 instrument. For the Dynamics Light Scattering (DLS) experiments Ar⁺ laser (1 W of power at 514.5 nm) with multiangle photometer-goniometer (BI 200SM) and BI-9000 correlator were used. DLS experiments were performed in methanol suspensions of BN powders. CONTIN algorithm [10] was employed for analysis of the DLS data. Characteristics of original h-BN (purity 99%) are described in detail in Section 3.1.

Results and discussion

Characteristics of original h-BN

As was shown by TEM, the original h-BN samples were tablets (Fig. 1) with diameter of 300–500 nm and thickness of 70–80 nm.

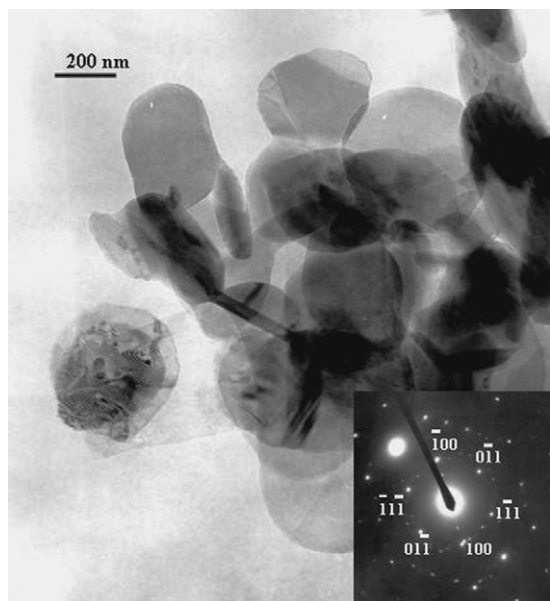


Fig. 1. TEM image and selected area electron diffraction for initial h-BN.

The reflection on selected area electron diffraction pattern corresponds to h-BN (Fig. 1) and suggests that the tablets are monocrystalline. The original h-BN XRD pattern indicates that the intensity of lines 002 and 004 is essentially higher than in the standard spectrum (texturing). In addition, lines 002 and 004 are noticeably widened. The line widening is due only to reduction in size of L of CSR: $L(002/004) = 84 \pm 15$ nm, $\varepsilon(002/004) = 0$. The lines in the direction of $[100]$ are not widened, allowing to conclude that $L(100) > 150$ nm.

The value of specific surface area (S) measured by BET of original h-BN sample is $S = 12$ m²/g. For flat tablets of thickness h , which is considerably smaller than the tablet diameter, the geometrical specific surface area is $S \approx 2/\rho h$ (here ρ is density). The thickness estimate based on this formula gives the value of $h = 71$ nm. Thus, the results on the tablet thickness are confirmed by three independent methods.

Therefore, we can conclude that the original h-BN samples are microcrystalline and have the shape of tablets with diameter of 300–500 nm and thickness of 70–80 nm. The flat side of tablets corresponds to the basal plane $[001]$.

The BN destruction and amorphization under ball milling

Fig. 2 shows the dependence of specific surface area measured by BET on the dose of mechanical treatment. At the initial stage of mechanical treatment specific surface area increases with increase of the dose, reaches maximum of about 400 m²/g (at the dose of 6–8 kJ/g), and then decreases as the dose continues to increase. Adsorption measurements in the broad interval of pressure have shown no microporosity at the initial stage of mechanical treatment.

Fig. 3a shows a microphotograph and microdiffraction pattern for the BN sample activated under the dose of 2.2 kJ/g. Apparently, the activated sample consists of long “rods” with 5–25 nm thickness. Selected area electron diffraction (SAED) patterns of the phase, formed during the ball milling (Fig. 3a), is characterized by the presence of the diffraction rings of polycrystalline boron nitride. The calculated interstitial distances for ring-type reflections are: 3.33, 2.16, 2.07 and 1.82 Å, which is in good agreement with the hexagonal boron nitride parameters. For the sample under the dose of

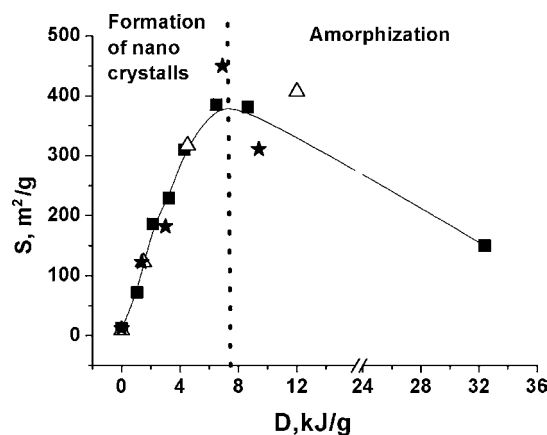


Fig. 2. Specific surface area of BN under ball milling.

4.3 kJ/g, the rods are significantly smaller (most rods are thinner than 5 nm). For this dose the SAD patterns show reflexes of polycrystalline boron nitride and an amorphous halo (primary data are not shown). Finally, for the sample under the dose of about 22 kJ/g (Fig. 3b) SAD corresponds to almost completely amorphous material.

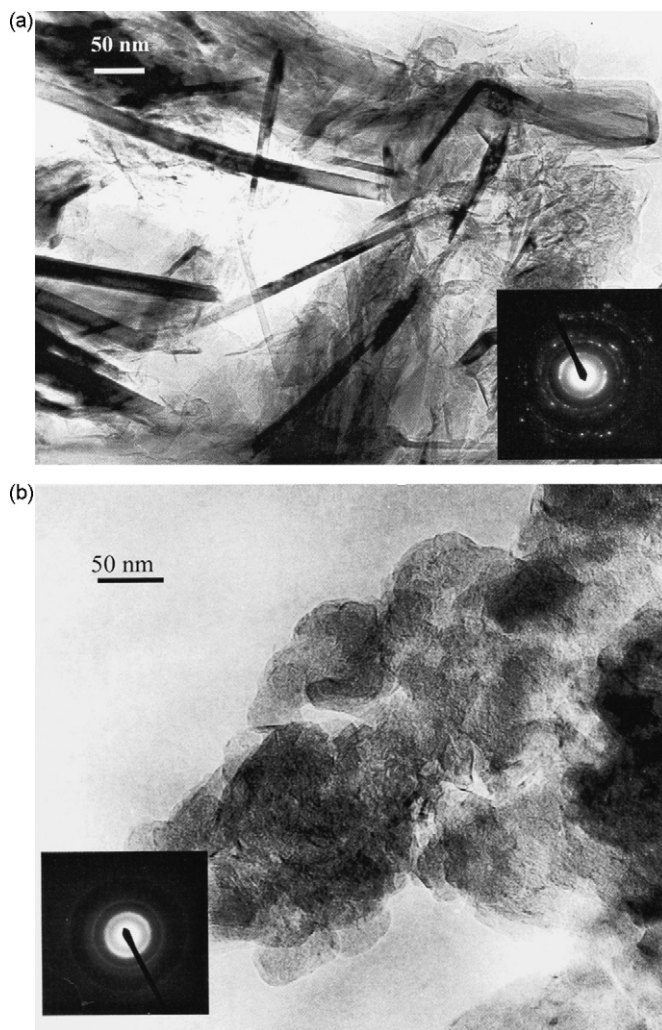


Fig. 3. TEM image and selected area electron diffraction for mechanically activated BN under the dose of 2.2 (a) and 22 (b) kJ/g.

Table 1

Comparison of the rod thickness obtained by TEM, BET and DLS techniques.

N	Dose (kJ/g)	TEM	BET	DLS
1	2.2	5–25 nm	10 nm	–
2	4.3	<5 nm	6 nm	5.5 nm

It is natural to assume that, in the absence of micropores, specific surface area is the external surface of the rods. Under the assumption that rods length considerably exceeds their thickness the specific surface area S is found to be about $4/\rho h$. Table 1 compares h values, calculated using this formula with the data of TEM. Clearly a satisfactory agreement is observed.

XRD patterns of mechanically activated BN under various doses are presented in Fig. 4. As doses of mechanical treatment increase, the BN lines widen. The lines 002 and 004 are widened much more than the line 100. For the dose of 2.2 kJ/g the CSR size estimated using Sherrer's formula for the line 002 was $L(002) \sim 30$ nm and for the line 100 it was $L(100) > 130$ nm. The anisotropy of roentgen line widening could indicate that rods are crystallographically oriented and their long side has a direction [100].

Under higher doses of mechanical activation, at the stage of reduction of specific surface two broad maxima are observed on diffractograms. The CSR formal estimation for diffractogram 7 in Fig. 4 results in $L(002) \sim 1.2\text{--}1.5$ nm.

Additional confirmation that the entire activated material at low doses consists of long rods is obtained from the Dynamic Light Scattering (DLS) spectroscopy. This method yields the translational and the rotational diffusion coefficients (D_{tr} , \mathcal{E} , respectively) of particles in solution (and/or suspension) from which the distribution of the apparent hydrodynamic radius and the shape of particles can be deduced. The shape of the size distribution function at different scattering angles for activated sample with the dose of 4.3 kJ/g reveals that: (1) BN particles have strongly anisotropic shape, (2) $D_{tr} = 3.97 \times 10^{-12} \text{ m}^2/\text{s}$ and $\mathcal{E} = 289.4 \text{ s}^{-1}$, (3) the rigid rod scattering model [11] suggests that the rods of the 450 nm in length and 5.5 nm in diameter is one possible solution that produces the values of \mathcal{E} and D_{tr} that are similar to experimental values. The value of 5.5 nm for sample 2 in Table 1 is similar to the values obtained from other methods.

In summary, mechanical treatment in the ball mill can be divided into two stages: under doses up to 6–8 kJ/g monocrystalline tablets of h-BN are cleaved to nanocrystalline rods, specific surface of which reaches hundreds of m^2/g ; under higher doses the amorphization processes start to appear and reduction of specific

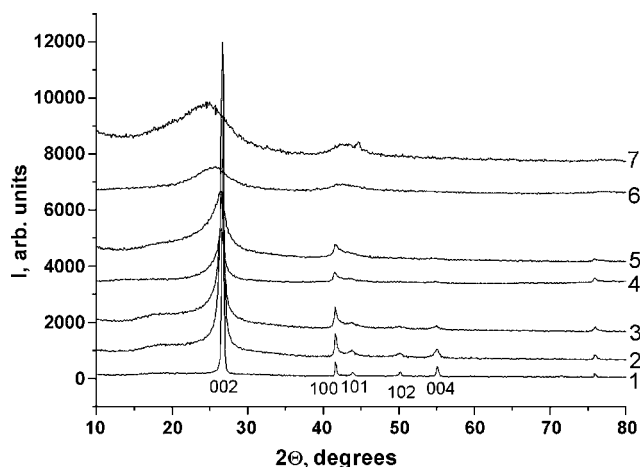


Fig. 4. X-ray diffraction patterns of BN after mechanical activation. Diffractograms correspond to doses: 0(1), 2.2 (2), 4.3(3), 6(4), 8.6 (5), 25 (6) and 32(7) kJ/g.

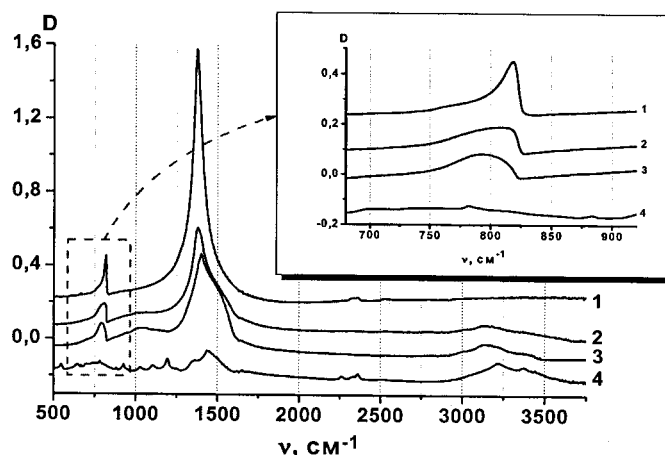


Fig. 5. FTIR spectra of initial h-BN sample (1) and ball milled samples with doses of 6.5 (2) and 22 (3) kJ/g as compared with the model FTIR pattern for B_2O_3 (4).

surface begins. By the moment when amorphization processes are dominant transversal dimension of “nanorods” is less than several nanometers.

It was found that the mechanical treatment causes a shift of XRD lines 002 and 004 towards small angles in addition to their widening. Also, the lines become anisotropic in shape (Fig. 4) under the treatment. The shift of lines 002 and 004 towards small angles points to the increase in the d_{002} distance between basal planes in BN. By the dose of 10 kJ/g, the distance estimated by position of line 002 maximum, d_{002} , increases from 0.3343 to 0.3365 nm. The anisotropy of the line 002 indicates possible formation of several fractions, differing by the extent of lattice “swelling”. It appeared that the shape of line 002 can be described satisfactory with the assumption of three or four fractions present. The more pronounced the lattice “swelling” is in a fraction, the wider the line in this fraction is.

“Swelling” of the mechanically activated BN lattice has also been confirmed by FTIR spectroscopy. The FTIR spectra of original h-BN sample have two bands at ~ 820 and $\sim 1370 \text{ cm}^{-1}$ (Fig. 5). According to [12], the band with the maximum at 1370 cm^{-1} corresponds to in plane vibration and the band at 817 cm^{-1} corresponds to out-of-plane vibrations. Fig. 5 shows that the mechanical activation results in a shift of the band from 820 cm^{-1} towards low frequencies by about 20 cm^{-1} . The shift of this band is indicative of the increase in the interlayer distance d_{002} [13].

Mechanical activation also results in appearance of new bands in FTIR spectra at 1030 , 1500 , and 3150 cm^{-1} . Control experiments

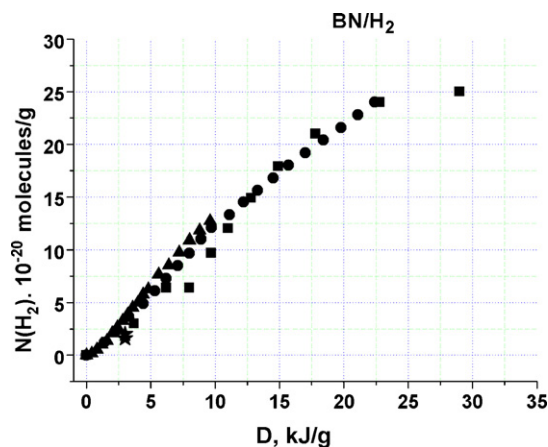


Fig. 6. Consumption of H_2 during ball milling of BN. H_2 pressure is $(3\text{--}5) \cdot 10^4 \text{ Pa}$.

Table 2
The depth (α , %) of BN + H₂O reaction at different temperatures.


Dose (kJ/g)	α_1 ($T = 20^\circ\text{C}$)	α_2 ($T = 70\text{--}90^\circ\text{C}$)
2.2	3	–
6.5	5	13
22	3	36
32	17	56

have shown that the appearance of new bands at 1500 and $\sim 3200\text{ cm}^{-1}$ may be attributed to B₂O₃. Boron oxide emerges in the samples, probably, as a result of the activated BN hydrolysis by water vapors from atmosphere during storage (see Section 3.4).

Mechanochemical hydrogenation of BN

Fig. 6 shows the dependence of the amount of absorbed hydrogen molecules on the dose of mechanical treatment. The rate of hydrogen absorption is nearly constant up to the doses of about 8 kJ/g and then it slightly decreases with the increase of the dose. Maximum amount of absorbed hydrogen under experimental conditions is 0.8 wt%.


Under the dose of 8 kJ/g the specific surface area appears to be equal to $S = 250\text{ m}^2/\text{g}$ and the amount of absorbed hydrogen molecules is $N = 1.3 \times 10^{21}$ molecules/g. This corresponds to the surface filling N/S with about 1×10^{15} hydrogen atoms per cm^2 , i.e. the filling is close to monolayer type of filling. After hydrogen chemisorption, the BN (band 2600 cm^{-1}) and NH (band 3086 cm^{-1}) groups formation was observed by FTIR method. It can be assumed that hydrogen interacts with disrupted bonds of $\text{--B}\cdots\text{N--}$, that inevitably appear upon cleavage of boron nitride particles with formation of “nanorods” according to the reaction



Upon heating of hydrogenated samples to 800°C the gases of H₂ and NH₃ are released.

Hydrolysis of mechanically activated h-BN

Original boron nitride is chemically inert, including its zero sensitivity to oxidation up to 1000°C . After mechanical activation BN acquires the ability to interact with water at room temperature according to the reaction



Ammonia formation was registered organoleptically and by chemical analysis. The appearance of B₂O₃ was confirmed by observation of absorption bands in FTIR spectrum at 1500 cm^{-1} and in the region of $3000\text{--}3500\text{ cm}^{-1}$. The depth of the reaction 2 (determined by gravimetric technique) increases as the dose of mechanical treatment increases. It reaches 56% at the dose of 32 kJ/g (Table 2). The difference between results obtained with cold and hot water in

Table 2 is probably due to formation of the glass-like modification of boron oxide, which is practically insoluble in cold water and is soluble upon heating above 60°C .

The most disordered part of activated boron nitride is involved in the reaction 2 with water. The XRD line of BN observed before the hydrolysis does not disappear after interaction with water, but becomes narrower.

Conclusions

Two processes take place during mechanical treatment of h-BN monocrystals. At the initial stage of mechanical treatment, the main process is cleavage of boron nitride plates in the plane (001) and formation of crystallographically oriented nanodimensional rods. The external specific surface of the rods reaches $400\text{ m}^2/\text{g}$.

The particle cleavage stimulates boron nitride hydrogenation (reaction 1) with formation of --BH and HN-- groups in a concentration similar to monolayer. The detailed mechanism of amazing processes of “oriented” cleavage requires further investigation.

The second process happening during the mechanical treatment is disordering of the BN crystalline structure. This is revealed in the increase of interlayer distance d_{002} , registered by XRD and FTIR techniques. It is possible that the lattice “swelling” is due to the processes of shifting along the plane (001), resulting in the loss of mutual orientation of these planes and boron nitride transition to the turbostratic and amorphous structures. Amorphization of BN is accompanied by the emergence of chemical activity during interaction with water (reaction 2). As a result of mechanical activation the depth of reaction 2 is near 60% even at 100°C , whereas for hydrating of non-activated BN the temperature has to be raised to 1000°C .

Acknowledgements

The work was carried out under financial support of Presidium RAS Program (no. 08-P), RFBR (grant 07-03-00610) and INTAS (grant 05-1000005-7672).

References

- [1] J. Tomas Jr., N.E. Weston, T.E. O'Connor, J. Am. Chem. Soc. 84 (1963) 4619.
- [2] Z.P. Xia, Z.Q. Li, J. Alloys Compd. 436 (2006) 170.
- [3] Y. Chen, L.T. Chadderton, J.F. Gerald, J.S. Williams, Appl. Phys. Lett. 74 (1999) 2960.
- [4] A.N. Streletskii, D.G. Permenov, I.V. Povstugar, S.N. Mudretsona, I.V. Berestetskaya, Chem. Sustainable Dev. 15 (2007) 175 (in Russian).
- [5] J.Y. Huang, H. Yasuda, H. Mori, J. Am. Ceram. Soc. 83 (2000) 403.
- [6] X.J. Du, F.Q. Guo, K. Lu, Nanostruct. Mater. 5 (1996) 579.
- [7] P.Yu. Butygin, I.K. Pavlichev, Reactivity Solids 1 (1986) 361.
- [8] P.Yu. Butygin, A.N. Streletskii, I.V. Berestetskaya, et al., Colloid J. 63 (2001) 639.
- [9] E.V. Shelekhov, Proceeding of National Conference on X-ray, SR, Neutrons and Electrons Application for Mat. Sci. Investigation, Dubna, V.3, 1997, p. 316 (in Russian).
- [10] K.M. Zero, R. Recora, Macromolecules 15 (1982) 87.
- [11] B.J. Berne, R. Pecora, Dynamic Light Scattering, Wiley, New York, 1976.
- [12] R.J. Nemanich, S.A. Solin, R.M. Martin, Phys. Rev. B23 (1981) 6348.
- [13] A.S. Rozenberg, Yu.A. Sinenko, N.V. Chukanov, J. Mater. Sci. 28 (1993) 567.